



# SYNTHESIS AND STRUCTURAL CHARACTERIZATION OF LEAD OXIDE

P. B. Taunk<sup>1</sup>, R. Das<sup>2</sup>, D. P. Bisen<sup>3</sup>, Raunak Kumar Tamrakar<sup>4</sup>,

Nootan Rathor<sup>5</sup>

<sup>1</sup> Department of Physics, Govt. Digvijay Autonomous PG College,  
Rajnandgaon, Chhattisgarh, (India)

<sup>2,4</sup> Department of Applied Physics, Bhilai Institute of Technology,  
Near Bhilai House, Durg (C.G.) (India)

<sup>3,4</sup> School of Studies in Physics and Astrophysics,

Pt. Ravishankar Shukla University, Raipur (C.G.) (India)

<sup>5</sup> Department of chemistry, Govt. V.Y.T.PG Autonomous College, Durg, (C.G.), (India)

## ABSTRACT

The present paper reports the synthesis and structural characterization of lead oxide. The sample was prepared by Chemical route method using TEA as capping agent. The particle size of prepared sample was calculated by XRD technique and Confirmed by Scanning electron microscope. The average crystal size of the lead oxide was 15-20nm range

**Keywords:** Lead oxide, XRD, SEM.

## I. INTRODUCTION

Nanomaterials are those which can be defined as the size lies within the nanometric range i.e. from one to a hundred nanometers [1,2]. The nano materials can be obtained by special procedures of the materials. In this range nanomaterials behave differently against its normal forms considerably from molecules and atoms. The physical, chemical, electrical and optical properties of these materials and size and shape dependent and they often exhibit important differences in the bulk properties [3-4]. The materials at such scale have attracted many workers in various fields from material science to biotechnology and genetics. They are used in a variety of different areas, such as electronic, magnetic and optoelectronic, biomedical, pharmaceutical, cosmetic, energy, environmental, catalytic, and materials applications[5-9].

Different techniques to synthesized nano range phosphor such as spray plasma-enhanced chemical vapor deposition [10], sol gel [11], sputtering [12]; pyrolysis [13], solid state reactions[14-19], co- precipitation [Bisen et al 2009] and combustion [20-23] etc have been used, but in recent times much interest has been generated around the chemical route technique. The technique is simple cost; effective, reproducible and the material are readily available [24-27].The technique is simple cost; effective, reproducible and the material are readily available

Lead oxides have many applications such as usage in dye, glass industry (lead glasses), piezoelectric ceramics, super capacitors and lead acid batteries specially as in nano particle. Nanometer-sized particles of metal coordination polymers are fascinating to explore, since their unique properties are controlled by the large number of surface molecules, which experience an entirely different environment than those in a bulk crystal. Several studies have been reported about the synthesis of PbO nanopowders [24-27], but if we look them carefully, morphology of finally products is very different from each other. On the other hand, the aim of this study is to demonstrate the optical and structure properties of the finally nano range lead oxide.

## II. EXPERIMENTAL PROCEDURE

**2.1. Powder Preparation:** For making reaction solution 0.04M aqueous solution of lead nitrate is mixed with 0.08M aqueous solution of sodium hydroxide (all AR grade 99.9% pure). After, we have added 3 ml TEA in the solutions [14]. The reaction solution is allowed to stand for 20 to 24 hours. The powder is thoroughly washed out (more than 8 times) with distilled water. It is filtered and dried in sunlight. It is then annealed in hot air oven at 290° C. The resultant effect is the colour of the powder appeared yellow [27,28].

## III. RESULTS AND DISCUSSION

**3.1 X- Ray Diffraction (XRD) Result:** The XRD pattern of the sample is shown in figure 1. The XRD pattern recorded lead oxide. The width of the peak increases as the size of the particle decreases. The size of the particle has been computed from the full width half maximum (FWHM) of the intense peak using Scherer formula. Particle size of sample in the range 17 nm is found. Formula used for calculation is [29]

$$D = \frac{0.9\lambda}{\beta \cos \theta}$$

Here D is particle size,  $\beta$  is FWHM (full width half maximum),  $\lambda$  is the wavelength of X ray source and  $\theta$  is angle of diffraction

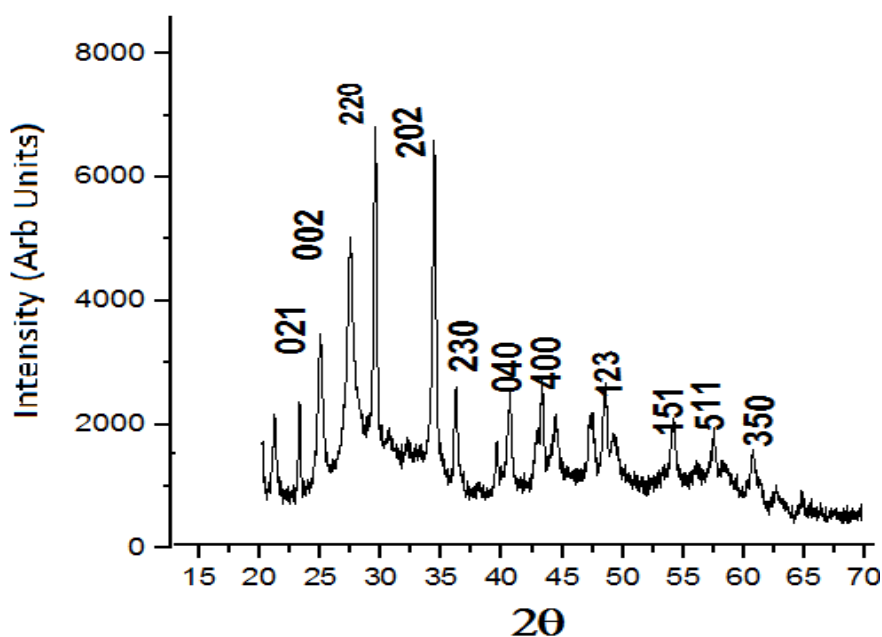


Fig 1 X-ray diffraction pattern of lead oxide

### 3.2 Scanning Electron Microscope (SEM)

For surface morphology and particle size analysis was cleared by SEM analysis (figure 2). Here the prepared sample shows good morphology and connectivity with grain. Here the particles are nano crystalline. Its is looks like rod type.

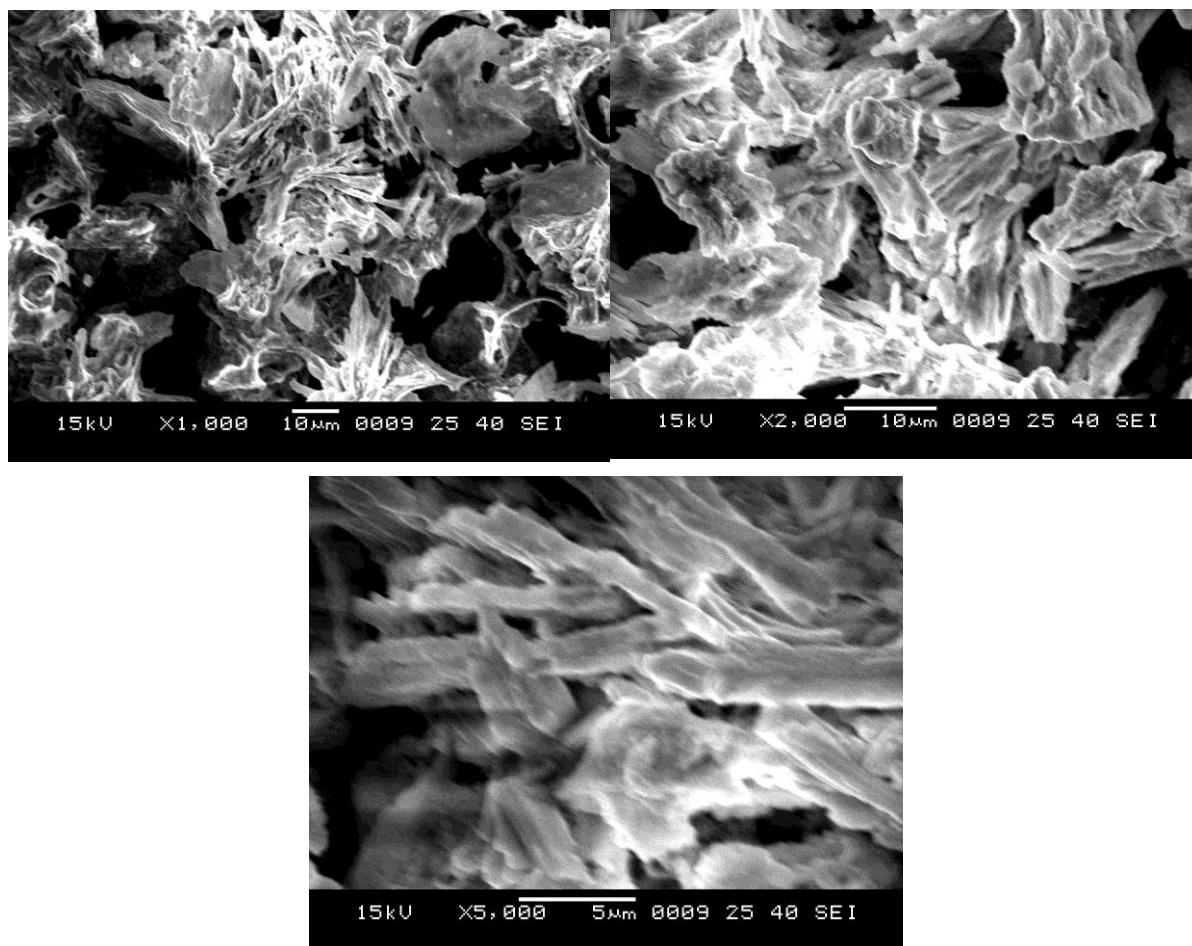


Figure 2. SEM image of lead oxide

## IV. CONCLUSIONS

Lead oxide has been successfully prepared by co-precipitation method using lead nitrate and sodium hydroxide with TEA as complexing agent. The particle size was found 17-20 nm range. Plate and powder like morphology showed in SEM images. Particle size was obtained in nano range.

## REFERENCES

- [1]. Keating C. D., Natan M. (2003). Striped Metal Nanowires as Building Blocks and Optical Tags. *Adv. Mater.*, 15: 451-454.
- [2]. R. K. Tamrakar, D. P. Bisen, Optical and kinetic studies of CdS: Cu nanoparticles, *Res. Chem. Intermed.* 39 (2013) 3043–3048.

- [3]. R. K. Tamrakar, Studies on Absorption Spectra of Mn Doped CdS Nanoparticles, (LAP Lambert Academic Publishing, Verlag, 2012). ISBN 978-3-659-26222-7.
- [4]. D. P. Bisen, R. Sharmab, N. Brahme, R. K. Tamrakar. Effect of Temperature on the synthesis Of Cds:Mn doped nanoparticles, Chalcogenide Letters Vol. 6, No. 9, September 2009, p. 427 – 431.
- [5]. R. K. Tamrakar, D. P. Bisen, Optical and kinetic studies of CdS: Cu nanoparticles, Res. Chem. Intermed .39 (2013) 3043–3048
- [6]. R. K. Tamrakar, D. P. Bisen, N. Bramhe, J. Radiat. Res. Appl. Sci., 7 (2014), pp. 550–559
- [7]. K. Upadhyay, R.K. Tamkrakar, V. Dubey, Superlattices Microstruct., 78 (2015), pp. 116–124
- [8]. Yang Y., Wang X.H., Sun C.K., Li L.T., Structural and optical properties of ZnO nanoparticles synthesized at different pH Values J. Appl. Phys.105 (2009) 094304
- [9]. Tamrakar R. K., Bisen D. P. Sahu I. and Bramhe N. (2014b), Raman and XPS studies of Combustion Route Synthesized Monoclinic Phase Gadolinium Oxide phosphors, Advance Physics Letters,2349-1108, Vol 1, Issue 1,Page1-5, 2014.
- [10]. Kim Y. J. And Kim H J (1999) ,”Trapped oxygen in the grain boundaries of ZnO polycrystalline thin films prepared by plasma-enhanced chemical vapour deposition “ mat lett 41 159- 153.
- [11]. Bao D, Gu H and Kuang A. (1988) ”Sol Gel-Derived C-axis Oriented ZnO Thin Films “ Thin Solid films. 312:37-39
- [12]. Subramanya T. K., Naidu B. S., and Uthanna S (2000 )“physical Properties of Zinc Oxide Film Prepared By De-reactive Magnetron Sputtering at Different Sputtering Pressures”. Cyst Res, Tectnol. #5:1193-1202.
- [13]. Santana G.; vacio Y et al (1999)”Structural and optical properties of (Zno)x (cdo)1-x Thin Fimss Obtained by spray pyrolysis” Superficies . 9:300-320
- [14]. Sahu I. P., Bisen D. P., Brahme N., Tamrakar R K , Shrivastava R, (2015a) Luminescence studies of dysprosium doped strontium aluminate white light emitting phosphor by combustion route, Journal of Materials Science: Materials in Electronics 26 (11), 8824-8839.
- [15]. Sahu I. P., Chandrakar P., Baghel R. N., Bisen D. P., Brahme N., Tamrakar R. K., (2015b) Luminescence properties of dysprosium doped calcium magnesium silicate phosphor by solid state reaction method, Journal of Alloys and Compounds 649, 1329-1338
- [16]. Sahu I. P., Bisen D. P., Brahme N., Tamrakar R K , (2015c) Luminescence enhancement of bluish-green  $\text{Sr}_2\text{Al}_2\text{SiO}_7: \text{Eu}^{2+}$  phosphor by dysprosium co-doping, Journal of Luminescence 167, 278-288
- [17]. Tamrakar R. K., Bisen D. P., Robinson C. S., Sahu I. P., and Brahme N.(2014), Ytterbium Doped Gadolinium Oxide ( $\text{Gd}_2\text{O}_3: \text{Yb}^{3+}$ ) Phosphor: Topology, Morphology, and Luminescence Behaviour in Hindawi Publishing Corporation, Indian Journal of Materials Science Volume (2014 ), Article ID 396147, 7,<http://dx.doi.org/10.1155/2014/396147>.
- [18]. Tamrakar R. K., Bisen D. P., Sahu I. P., and Brahme N. (2014a), UV and gamma ray induced thermoluminescence properties of cubic  $\text{Gd}_2\text{O}_3: \text{Er}^{3+}$  phosphor, Journal of Radiation Research and Applied Sciences, 30 July (2014), DOI: 10.1016/j.jrras.2014.07.003

- [19]. Tamrakar, R. K., Bisen, D. P., & Brahme, N. (2014c) Influence of  $\text{Er}^{3+}$  concentration on the photoluminescence characteristics and excitation mechanism of  $\text{Gd}_2\text{O}_3:\text{Er}^{3+}$  phosphor synthesized via a solid-state reaction method, *Luminescence (Impact Factor: 1.27)*, 11/2014; DOI: 10.1002/bio.2803
- [20]. Tamrakar, R. K., Tiwari N., Kuraria R. K., dubey V. & Upadhyay K.,( Effect of annealing temperature on thermoluminescence glow curve for UV and gamma ray induced  $\text{ZrO}_2:\text{Ti}$  phosphor, *Journal of Radiation Research and Applied Sciences* (2014), [http://dx.doi.org/ 10.1016/j.jrras.2014.10.005](http://dx.doi.org/10.1016/j.jrras.2014.10.005)
- [21]. Tamrakar, R. K., Bisen, D. P., & Brahme, N. (2014a) Characterization and luminescence properties of  $\text{Gd}_2\text{O}_3$  phosphor. *Research on Chemical Intermediates*, 40, 1771-1779
- [22]. Tamrakar, R. K., Bisen, D. P., & Brahme, N. (2014b) Comparison of photoluminescence properties of  $\text{Gd}_2\text{O}_3$  phosphor synthesized by combustion and solid state reaction method, *Journal of Radiation Resea*
- [23]. Tiwari N., Kuraria R. K., Tamrakar R. K.:(2014) Thermoluminescence glow curve for UV induced  $\text{ZrO}_2:\text{Ti}$  phosphor with variable concentration of dopant and various heating rate, *Journal of Radiation Research and Applied Sciences* (2014), [http:// dx.doi.org/10.1016/j.jrras.2014.09.006](http://dx.doi.org/10.1016/j.jrras.2014.09.006).
- [24]. 10.Chen L. J., Zhang S. M., Wu Z. S., Zhang Z. J., Dang H. X.(2005). Preparation of PbS-type PbO nanocrystals in a room-temperature ionic liquid. *Mater. Lett.*, 59: 3119-3121.
- [25]. Salavati-Niasari M., Mohandes F., Davar F. (2009). Preparation of PbO nanocrystals via decomposition of lead oxalate. *Polyhedron.*, 28: 2263-2267
- [26]. Ferg E. E., Phangalala T., Dyl T. (2010). A new look at determining acid absorption of lead oxide used in the manufacturing of Pb-acid batteries. *J. Appl. Electrochem.*, 40: 383-391
- [27]. P. B.Taunk, R. Das and D. P. Bisen' Effect of the Concentration of TEA on the Formation of Lead Hydroxide Micro to Nano Particle, *Materials Science in Semiconductor Processing*, Volume 32, April 2015, Pages 49–54
- [28]. P .B. Taunk ,R Das ,D P Bisen , R. K. Tamrakar, Structural characterization and photoluminescence properties of zinc oxide nano particles synthesized by chemical route method, *Jorunal of radiation reseach and applied science* , Volume 8, Issue 3, July 2015, Pages 433-438
- [29]. A. Guinier, *X-ray diffraction*, Freeman, San Francisco, 1963.