



AN EXPERIMENTAL INVESTIGATION ON FLY ASH BRICK WITH NATURAL FIBRE

Kiruthika.N¹ , Niresh.B² , Ajith.T³ , Arularasan.J⁴ , Arjun.S⁵

¹ AP, Department of Civil Engineering, Sengunthar Engineering College,(INDIA)

²Student, Department of Civil Engineering, Sengunthar Engineering College,(INDIA)

³Student, Department of Civil Engineering, Sengunthar Engineering College,(INDIA)

⁴Student, Department of Civil Engineering, Sengunthar Engineering College,(INDIA)

⁵Student, Department of Civil Engineering, Sengunthar Engineering College,(INDIA)

Abstract

The use of brick masonry is common in our country. The important material for construction of infill walls and load bearing walls are Clay bricks, Fly ash bricks, Hollow blocks and the dividing of rooms is made possible by steel sheets, wooden pieces and glasses.

This investigation is carried out by materials like fly ash, coir fibre, and quarry dust for manufacturing of bricks. The fly ash class 'F' is used for manufacturing of bricks. The fly ash is the waste product from thermal power plants and it disposed in huge volumes. But it can be used as a resource material for manufacturing of bricks. In agricultural field waste materials are generated. Especially fibres having good mechanical properties, coir fibre and banana fibre and jute fibre are examples.

This investigation deals with manufacturing of bricks using fly ash and coir fibre as a resource materials from waste and cement as a binding material, and adding coir fibre of 0.4%, 0.8%, 1.2%, 1.6%. After the specimen preparation, compressive strength test and water absorption test are conducted. We conclude that the brick with 1.6% of addition of coir fibre have 4.11 N/mm² of compressive strength and 69.38 mm displacement of flexural strength. The maximum cost per brick Rs. 3.36. It is economical when compared to conventional bricks available in market.

Keywords: Bricks, Fly ash, Coir Fibre, Compressive Strength, Cement.

INTRODUCTION

In the present scenario an alternate for clay bricks is fly ash bricks which plays key role in the construction of framed structures because of its less weight which will reduce the dead weight of the structures, another advantage is low cost. Such fly ash bricks are not subjected to load bearing structures because of its slight reduction in compressive strength compare with nominal clay bricks. So majority of the fly ash bricks were used



in framed structure construction. In this study a concern to increase compressive strength using coconut fibre is carried out. A comparison has been carried out for the normal brick to fibre reinforced bricks. From the comparison the test result has shown a significant change in the compressive strength by the addition of coir fibre and the test result show significant changes in water absorption quality and other properties of fly ash bricks.

LITERATURE SURVEY

GIRISHA.C, SANJEEVAMURTHY, GUNTI RANGA SRINISVAS, Sep 2012, “Coconut coir Fibre: water absorption and mechanical properties”

- Natural fibres reinforced Epoxy composites were subjected to water immersion tests in order to study the effects of water absorption and the mechanical properties.
- Fibres in weight fraction 20%, 30%, and 40% were used for the fabrication of the composite.
- This test increases the volume fraction because of high cellulose content of the fibre.

SAKINA NAJMUDDIN SAIFEE, DIVYA MAHESHBAL LAD, May-2015 “Coir fibre; A best use of waste material”

- This paper is an attempt to make the best use of the waste material obtained from the coconut trees.
- The coir fibre is widely adopted as an engineering material due to its high tensile strength and elasticity.
- It is useful because of its physical and mechanical properties.

K.SARAVANA RAJA MOHAN, P.JAYABALAN, A.RAJARAMAN (2012) ., “Properties of Fly Ash Based Coconut Fibre Composite”.

- Ordinary portland cement 43 grade with fly ash showed an increase in compressive strength, split tensile strength, flexural strength and modulus of elasticity.
- Addition of coconut fibre in fly ash mixed concrete composite enhance the mechanical properties.
- Cement is replaced with five percentages (10,20,30,40 and 50%) of class F Fly ash.
- Four percentages of coconut fibres (0.15, 0.30, 0.45, and 0.60%) having 40mm length were used.



1.

1.1 MIX DESIGNATION

DETAILS	DESIGNATION
Conventional bricks	B
Addition 0.4%	B1
Addition 0.8%	B2
Addition 0.12%	B3
Addition 0.16%	B4

1.2 MIX PROPORTIONING

SAMPLES	FLY ASH (Kg)	QUARRY DUST (Kg)	CEMENT (Kg)	COIR FIBRE (Gm)
B	1.692	0.846	0.282	0
B1	1.692	0.846	0.282	10
B2	1.692	0.846	0.282	20
B3	1.692	0.846	0.282	30
B4	1.692	0.846	0.282	40

2. TEST FOR BRICKS:

2.1 COMPRESSIVE STRENGTH TEST

(7 DAYS)

S.No	SAMPLES	LOAD (KN)	STRENGTH(N/mm ²)
B	0	51.1	2.22
B1	0.4%	53.2	2.31
B2	0.8%	57.2	2.48
B3	0.12%	73.1	3.17
B4	0.16%	76.2	3.33




2.2 COMPRESSIVE STRENGTH TEST

(28 DAYS)

S.No	PROPORTIONS	LOAD (KN)	STRENGTH (N/mm ²)
B	0	80.8	3.51
B1	0.4%	85.2	3.70
B2	0.8%	90.6	3.93
B3	0.12%	93.9	4.08
B4	0.16%	94.7	4.11

2.3 COMPARISON OF COMPRESSIVE STRENGTH RESULTS

COMPARISON OF COMPRESSIVE STRENGTH RESULTS

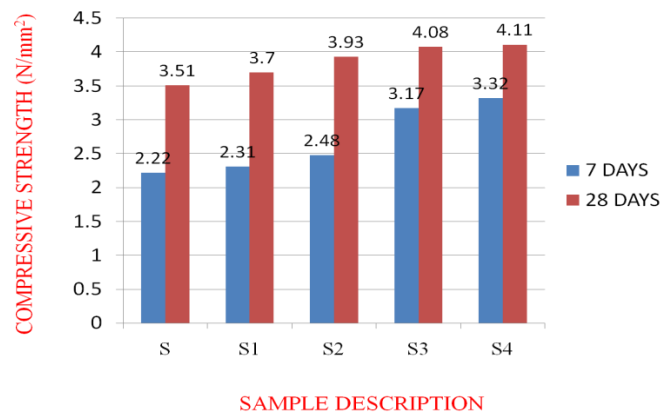

3.

3.1 WATER ABSORPTION TEST

(7 DAYS)

S.No	DRY WEIGHT(W1) Gm	WET WEIGHT(W2) Gm	WATER ABSORPTION %
B	2532	2589	2.25
B1	2545	2664	4.67
B2	2560	2670	4.29
B3	2618	2697	3.01
B4	2578	2709	2.25




3.2 WATER ABSORPTION TEST

(28 DAYS)

S.No	DRY WEIGHT(W1) Gm	WET WEIGHT(W2) Gm	WATER ABSORPTION %
B	2520	2650	5.15
B1	2546	2680	5.26
B2	2562	2688	4.91
B3	2592	2708	4.47
B4	2610	2718	4.13

3.3 COMPARISON OF WATER ABSORPTION TEST

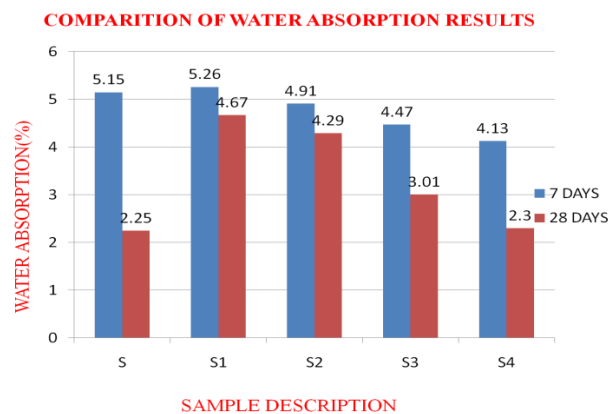


4. FLEXURAL STRENGTH TEST

(28 DAYS)

S.No	LOAD(KN)	DISPLACEMENT(mm)
B	6.6	50.47
B1	6.8	59.13
B2	7.0	59.54
B3	7.2	58.42
B4	7.2	69.38



4.1 FLEXURAL STRENGTH TEST RESULTS

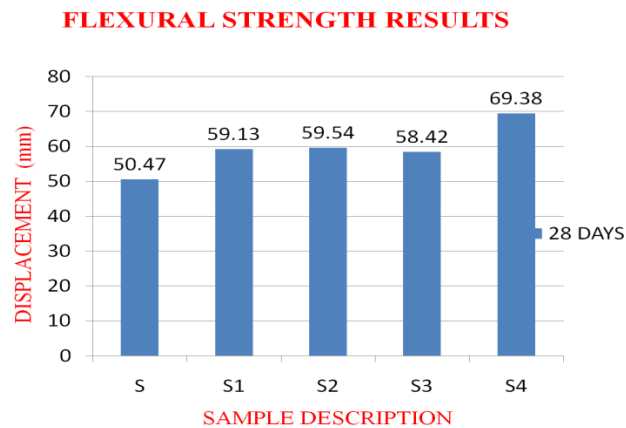

5. COST ANALYSIS OF BRICKS

BRICK	COST (Rs)
B	3.340
B1	3.345
B2	3.350
B3	3.355
B4	3.360

6. CONCLUSION

- The above results concludes that the compressive strength of fly ash bricks using coir fibre is 1.6% higher than the ordinary clay bricks, so this bricks can be effectively used for all construction purposes.
- In this report optimum value of the brick sample4(S4) was observed at the proportion of 60% of Fly ash, 10% of Cement ,30% of Quarry dust and 1.6% of coir fibre and the cost of that brick was Rs. 3.36 only.
- It is economical when compared to that of conventional bricks available in market.

7. REFERENCES

- Dr. H.P Singh (September 2013) – “Strength and Stiffness Response of Itanagar Fly Ash Reinforced with Coir Fibre” – International of Research in Innovative Science, Engineering and Technology, Volume - 2, Page no: 4500 – 4509.



- Girisha.C, Sanjeevamurthy, GuntiRangaSrinivas, (September 2012) -"Sisal/Coconut Coir Natural Fibres - Epoxy Composites: Water Absorption and Mechanical Properties" - International Journal of Engineering and Innovative Technology, Volume - 2. Page no: 166- 170.
- J.N Akhtar, J. Alam and M.N Akhtar (September 2010) - "An Experimental Study OnFibre Reinforced Fly Ash Based Lime Bricks"-International Journal of the Physical Sciences, Volume - 5(11), Page no: 1688-1695.
- Mohammad ShahidArshad, Dr. P.Y. Pawade (June 2014) - "Reuse of Natural Waste Material for Making Eight Weight Bricks" International Journal of Science and Technology Research, Volume - 3, Page no: 49 - 53.
- Nutan C. Patel, Prof. JayeshkumarPitroda(March 2013) "Fly Ash Brick: Glass Fibre the Innovative Concept for (letting Higher Strength brick" -International Journal of Research Innovative in Science. Engineering and Technology, Volume - 2, Page no: 1-8.
- R.K.Watile, S. K. Deshmukh, H.C.Muley (May 2014) - "Interlocking brick For Sustainable Housing Development" - International Journal of Science, Spirituality, Business and Technology, Volume - 2,Page no: 58 - 64.
- SakinaNajmuddinSaifee, DivyaMaheshbhai lad (May 2015) - "Coir Fibres: A best use of waste material" International Journal of Research and Development Organization, Volume - 2.
- Sanjay Salla, JayeshkumarPitroda (December 2012) - "A Comparative Review on: Effect of Natural Fibres Inclusion in Fly Ash Bricks" - Indian Journal of Research. Volume - 1, Page no: 62 - 64.
- ShardaDhadse, PranilaKumari and LJ. Bhagia (January 2008) - *¹Fly Ash Characterization, utilization and Government Initiatives in India - A review" Volume 67, Page no: 11 - 18.